

AD-A064 703

LEHIGH UNIV BETHLEHEM PA INST OF FRACTURE AND SOLID --ETC F/G 11/6  
RECENT PROGRESS IN UNDERSTANDING ENVIRONMENT ASSISTED FATIGUE C--ETC(U)  
JAN 79 R P WEI, G W SIMMONS  
IFSM-79-94

N00014-75-C-0543


NL

UNCLASSIFIED

1 OF 1  
AD  
A064703



END  
DATE  
FILMED  
4-79  
DDC

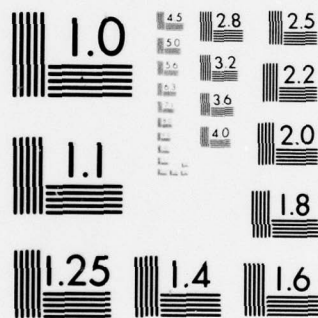

MICROCOPY RESOLUTION TEST CHART  
NATIONAL BUREAU OF STANDARDS-1963-A

79 02 12 094

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER IFSM-79-94 TR-8	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Recent Progress in Understanding Environment Assisted Fatigue Crack Growth,		5. TYPE OF REPORT & PERIOD COVERED Technical Report, No. 8
7. AUTHOR(s) R. P. Wei and G. W. Simmons		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Lehigh University Bethlehem, PA 18015		8. CONTRACT OR GRANT NUMBER(s) Contract N00014-75-C-0543
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Department of the Navy Arlington, VA		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 036-097
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) 12 18p.		12. REPORT DATE 11 January 1979
		13. NUMBER OF PAGES 11
		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) This document has been approved for public release and sale; its distribution is unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report) D D C RECEIVED FEB 16 1979 B		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Fracture Mechanics, Surface Chemistry, Corrosion Fatigue, Alloy Steel, Hydrogen Embrittlement, Aluminum Alloy		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Recent fracture mechanics and surface chemistry based studies have contributed to further understanding of environment assisted fatigue crack growth in high-strength alloys. The rate of fatigue crack growth in an aggressive environment, $(da/dN)_e$ , may be considered to be the sum of three components. $(da/dN)_e = (da/dN)_r + (da/dN)_{cf} + (da/dN)_{sc}$		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE  
S/N 0102-014-6601

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

407 099

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

$(da/dN)_f$  is the rate of fatigue crack growth in an inert environment, and, therefore, represents the contribution of "pure" fatigue.  $(da/dN)_{cf}$  represents a cycle-dependent contribution requiring synergistic interaction of fatigue and environmental attack.  $(da/dN)_{sc}$  is the contribution by sustained-load crack growth (i.e., stress corrosion cracking) at K levels above  $K_{Isc}$ . The cycle-dependent term has been shown to arise from the reaction of the environment with fresh crack surfaces produced by fatigue, and is a function of the extent of reaction during one loading cycle. For highly reactive alloy-environment systems, cracking response may depend also on the rate of transport of the aggressive environment to the crack tip. For gaseous environments, a formal basis for estimating pressure and frequency dependence has been developed. The framework and approach are expected to be applicable to other aggressive environments (such as, aqueous environments), and should provide a basis for the development of appropriate material evaluation and life prediction procedures.

ACCESSION for	
NTIS	White Section <input checked="" type="checkbox"/>
DDC	Buff Section <input type="checkbox"/>
UNANNOUNCED	<input type="checkbox"/>
JUSTIFICATION	
BY	
DISTRIBUTION/AVAILABILITY CODES	
Dist. Avail. and/or SPECIAL	
A	

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

RECENT PROGRESS IN UNDERSTANDING ENVIRONMENT ASSISTED  
FATIGUE CRACK GROWTH

BY

R. P. Wei and G. W. Simmons  
Lehigh University  
Bethlehem, PA 18015

This document has been approved for public release and sale;  
its distribution is unlimited.

Prepared for presentation at the Third International Conference  
on Mechanical Behaviour of Materials (ICM-3), Cambridge, England,  
August 20-24, 1979, and for publication in the Conference Proceedings.

RECENT PROGRESS IN UNDERSTANDING ENVIRONMENT ASSISTED  
FATIGUE CRACK GROWTH

R. P. Wei\* and G. W. Simmons\*\*  
Lehigh University  
Bethlehem, PA 18015 USA

\*Dept of Mechanical Engineering and Mechanics

\*\*Dept of Chemistry and Ctr for Surface and Coatings Research

INTRODUCTION

Metal fatigue has been well recognized as an important cause for failure of engineering structures. In most applications, fatigue damage results from the conjoint actions of the cyclically applied stress and external (chemical) environment, and is therefore a time dependent phenomenon. Understanding of this load-environment interaction in fatigue is essential to the formulation of rational life prediction procedures and to the development of realistic materials evaluation and qualification tests. Quantitative characterization and understanding, however, have been hampered by the complexity of the phenomenon, by difficulties in separating the effects associated with crack initiation from those associated with crack growth, and by the influence of external chemical environments on both the initiation and growth processes.

With the increased emphasis placed on fatigue crack growth in many applications since the early 1950's and the development of fracture mechanics technology, separate considerations of the processes associated with fatigue crack growth evolved more or less naturally. This separation has provided better definition and focus, and has been by and large beneficial in terms of developing understanding of environment assisted fatigue crack growth. In this paper, the background and recent progress in understanding environment assisted fatigue crack growth are described. Implications of current understanding in terms of service performance and life prediction procedures are considered.

BACKGROUND

Studies of the influence of environment on fatigue crack growth began in the mid 1960's and have continued throughout the past 15 years. The results from the various studies have been reviewed and summarized in a number of papers (Gallagher and Wei, 1972; McEvily and Wei, 1972; Wei, 1970) and in the proceedings of conferences (Fatigue Crack Propagation, 1967; Corrosion Fatigue, 1972). Most of the early studies were directed at characterizing fatigue crack growth response, and at examining the influences of different loading variables on environment assisted fatigue crack growth. Results from these early studies served to demonstrate the complexity of the problem, and showed that many of the observed effects of loading variables can be traced directly to their interactions with the environment (McEvily and Wei,

THIS PAGE IS BEST QUALITY PRACTICABLE  
FROM COPY FURNISHED TO DDC

1972; Wei, 1970). It became apparent also that a better understanding of the underlying processes for environment assisted fatigue crack growth is needed to provide a rational basis for the interpretation of crack growth data. A number of issues began to crystallize by the early 1970's. These issues relate to the reported differences in response to frequency and waveform for aluminum alloys (Bradshaw and Wheeler, 1968; Hartman and coworkers, 1967; Hudak and Wei, 1972; Wei, 1968) and steels (Barsom, 1972; Gallagher, 1971; Wei, Talda and Li, 1967), the relationship between environment assisted sustained-load crack growth (stress corrosion cracking) and fatigue crack growth (corrosion fatigue) (Miller, Hudak and Wei, 1973; Speidel and coworkers, 1972; Wei and Landes, 1969), and the cause or mechanism for environment assisted fatigue crack growth below the so-called stress corrosion cracking threshold ( $K_{Isc}$ )<sup>1</sup> (Wei and Speidel, 1972; Wei and Simmons, 1977). The most important issue, insofar as it relates to phenomenological understanding of load-environment interactions, appears to be the identification of the rate controlling process for environment assisted crack growth (Simmons, Pao and Wei, 1978; Wei and Simmons, 1977). The possible sequential processes involved in environment assisted crack growth are illustrated schematically in Fig. 1, for example, for a ferrous alloy exposed to a hydrogenous gas (Wei, 1979). The need for and development of a fundamental approach for addressing these issues are discussed by Wei and Simmons (1977), Wei (1979) and Williams, Pao and Wei (1979).

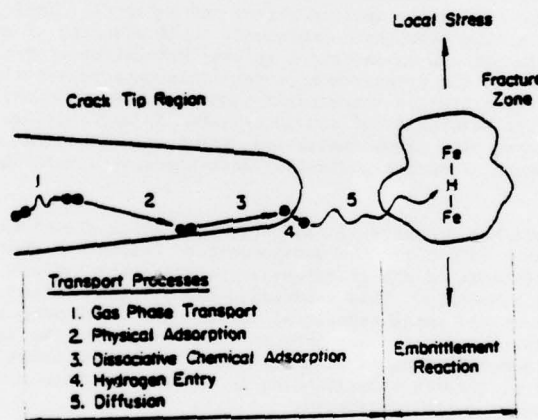


Fig. 1. Schematic illustration of various sequential processes involved in embrittlement by external gaseous environments. (Embrittlement reaction is depicted by the Fe-H-Fe bond.) (After Wei, 1979.)

Using an integrated interdisciplinary approach, Simmons, Pao and Wei (1978) sought to identify the rate controlling process for crack growth in water/water vapor for a high-strength (AISI 4340) steel. To this end, sustained-load crack growth experi-

<sup>1</sup> $K_{Isc}$  is the apparent threshold stress intensity (K) level for stress corrosion cracking and is defined as the asymptotic value of K as the rate of crack growth under sustained load approaches zero (Brown and Beacham, 1965; Wei, Novak and Williams, 1972).

ments were carried out in hydrogen and in water to determine the kinetics of crack growth as a function of temperature. Companion experiments were carried out on the same steel to determine the kinetics of water-metal surface reactions using Auger electron spectroscopy (AES). These studies were supplemented by detailed fundamental studies of reactions of water vapor with iron single crystals by AES and LEED (low energy electron diffraction) (Dwyer, Simmons and Wei, 1977), and by AES analysis of the elemental composition of fracture surfaces produced by environment assisted crack growth (Wei and Simmons, 1976). Through these coordinated interdisciplinary studies and comparisons of activation energies for crack growth and for surface reactions, the rate controlling process for crack growth was identified to be a slow step in the reaction of water/water vapor with iron and, perhaps, iron carbide (Dwyer, Simmons and Wei, 1977; Simmons, Pao and Wei, 1978). This reaction step is associated with the nucleation and growth of oxide on the surface, and the presumed concomitant production of hydrogen (Simmons, Pao and Wei, 1978).

Having identified the rate limiting process for sustained-load crack growth for this high-strength steel in water/water vapor, Pao, Wei and Wei (1979) examined its implication in terms of environment assisted fatigue crack growth response. Their results indicated that both steady-state and nonsteady-state crack growth response can be adequately explained in relation to the kinetics of surface reactions. Based on this success, the integrated interdisciplinary approach has been extended to the study of environment assisted fatigue crack growth response in an aluminum alloy (Wei and coworkers, 1979). This later study expands on an earlier suggestion by Bradshaw and Wheeler (1968) that the enhancement of fatigue crack growth in aluminum alloys by water vapor is determined by the exposure (pressure x time) during each load cycle. The results from these recent investigations are summarized and their engineering significance are considered.

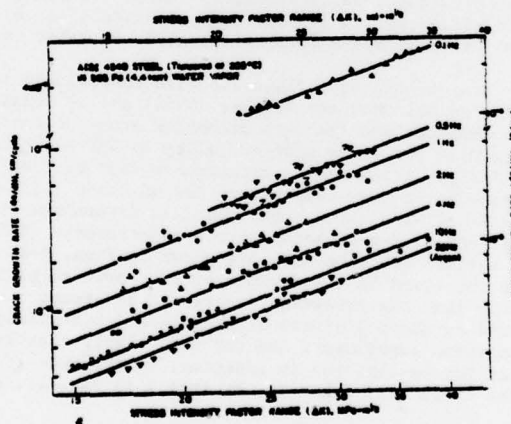


Fig. 2. Room temperature fatigue crack growth kinetics on AISI 4340 steel tested in dehumidified argon and in water vapor (below  $K_{Isc}$ ) at  $R = 0.1$ . (After Pao, Wei and Wei, 1979.)

#### RECENT PROGRESS IN UNDERSTANDING ENVIRONMENTAL EFFECT

Pao, Wei and Wei (1979) examined the effect of cyclic-load frequency (0.1 to 10 Hz) on fatigue crack growth in a high-strength (AISI 4340) steel tested in water vapor at room temperature. A water vapor pressure of 585 Pa was selected to preclude capillary condensation at the crack tip. Steady-state crack growth data from this study are shown in Fig. 2, and confirm the existence of a substantial effect of frequency at  $K_{max}$  levels well below that required for producing significant crack growth under sustained loads (that is, below  $K_{Isc}$ ) (Barsom, 1972; Gallagher, 1971). Fractographic data indicated that at the higher frequencies (namely, 10 Hz), the fracture surface morphology was akin to that for "pure" (mechanical) fatigue. At the lower frequencies (that is, below 1 Hz), on the other hand, the morphology exhibited increasing amounts of intergranular separation along prior-austenite grain boundaries that is typical for sustained-load crack growth in water/water vapor (Simmons, Pao and Wei, 1978). These observations, taken in conjunction with previous studies, suggested that the steady-state fatigue crack growth rate in an aggressive environment is composed of two components — one for "pure" fatigue and the other representing the environmental contribution. Because the rate controlling process has been identified to be a slow-step in the water-metal surface reaction in this case, the environmental component is expected to depend on the time available for this reaction (namely, the cyclic load period) and on the reaction kinetics. In other words, the extent of crack growth during one loading cycle is expected to be proportional to the extent of reaction (or surface coverage) during that cycle. Based on data on the kinetics of surface reactions (Simmons, Pao and Wei, 1978), the environment contribution<sup>2</sup> should vary almost linearly with the cyclic load period or inversely with frequency, over the range of frequencies used in their investigation, Figs. 3 and 4 (Pao, Wei and Wei, 1979). At high frequencies, environmental effect should be essentially negligible; at low frequencies, it should reach a maximum or a saturation value. This general trend is consistent with data reported by Gallagher (1971) for fatigue crack growth in a high-strength (HY-80) steel in 3.5 pct NaCl solution (Fig. 5), and by Bradshaw and Wheeler (1968) on an aluminum (DTD 5070A) alloy in water vapor.

To further verify the concept of surface reaction control and to follow up on the earlier suggestions by Bradshaw and Wheeler (1968) and by Hudak and Wei (1972), a combined surface chemistry and fracture mechanics study of fatigue crack growth in water vapor was carried out on an aluminum alloy by Wei and Simmons and their coworkers (1979). Fatigue crack growth experiments were carried out as a function of water vapor pressure at room temperature for an Al-Cu (2219-T851) alloy. The reactions of this alloy with water vapor was also determined by Auger electron spectroscopy (AES) and by x-ray photoelectron spectroscopy (XPS). The fatigue crack growth and surface reaction data are shown in Figs. 6-8. Comparison of Figs. 7 and 8 indicates the trend in the fatigue crack growth and surface reaction data are similar, except that the exposures (expressed as pressure x time or pressure/frequency) differed by about 3 orders of magnitude. Recognizing that at the low pressures used in these experiments and for this highly reactive system, the environmental effect may be limited, in addition, by the rate of transport of the environment to the crack tip<sup>3</sup> (that is, by step 1 in Fig. 1), an estimate of this

<sup>2</sup>The environmental contribution is represented by the difference of two empirical constants,  $C - C_0$ , determined by least-squares fit to the data in Fig. 2 using  $da/dN = C\Delta K^2$ . This empirical relationship provided a convenient means for representing these data, but does not have general validity.

<sup>3</sup>Transport limitation has been suggested by the companion fractographic observations (Wei and coworkers, 1979).

influence has been made (Wei and coworkers, 1979). This estimate showed that by incorporating the transport process, good correlation between surface reaction kinetics and the rate of environment assisted fatigue crack growth in the aluminum alloy can be obtained (see Fig. 9).

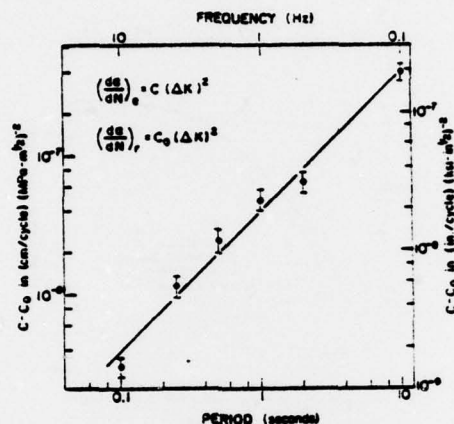


Fig. 3. Environment dependent component of fatigue crack growth parameter as a function of cyclic load period for AISI 4340 steel tested in water vapor at room temperature. (After Pao, Wei and Wei, 1979.)

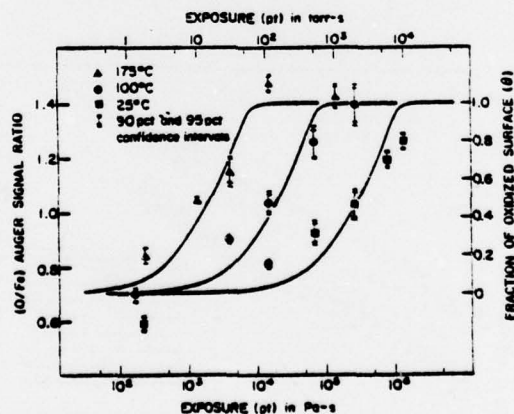


Fig. 4. Kinetics of reaction of AISI 4340 steel with water vapor at three temperatures. (The steel surface was ion etched prior to each exposure to water vapor.) (After Simmons, Pao and Wei, 1978.)

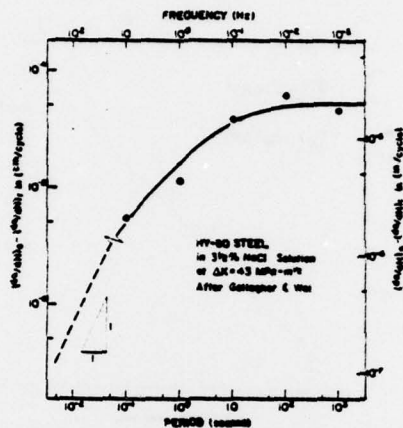


Fig. 5. Environment dependent component of fatigue crack growth rate as a function of cyclic load period for HY-80 steel tested in 3.5 pct NaCl solution at room temperature. (After Gallagher, 1971; Gallagher and Wei, 1972; Pao, Wei and Wei, 1979.)

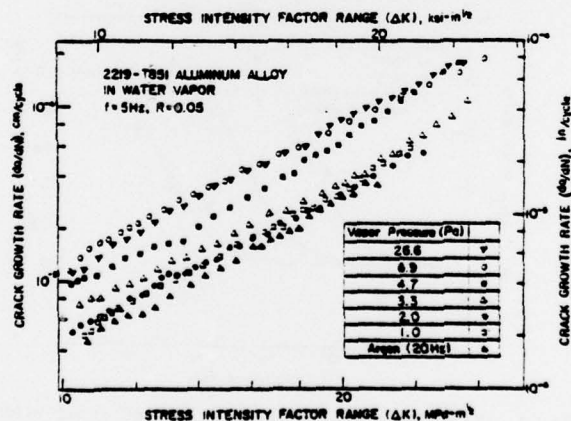


Fig. 6. Influence of water vapor pressure on the kinetics of fatigue crack growth in 2219-T851 aluminum alloy at room temperature. (After Wei and coworkers, 1979.)

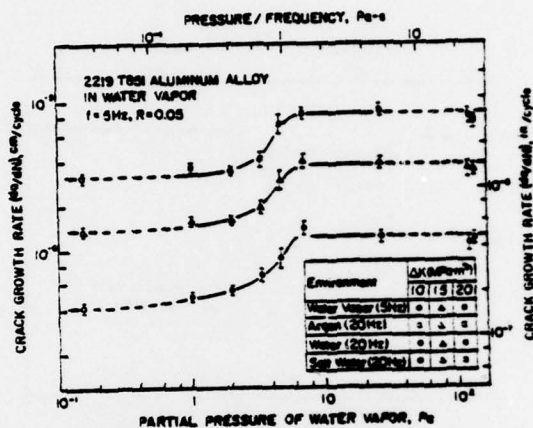


Fig. 7. Influence of water vapor pressure (or pressure/frequency) on fatigue crack growth rate in 2219-T851 aluminum alloy at room temperature. (After Wei and coworkers, 1979.)

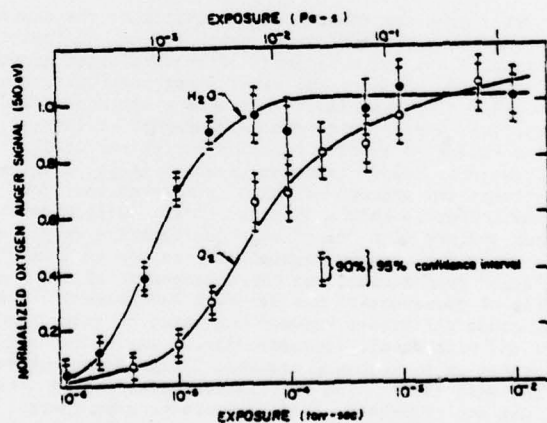


Fig. 8. Kinetics of reactions of 2219-T851 aluminum alloy with oxygen and with water vapor at room temperature. (After Wei and coworkers, 1979.)

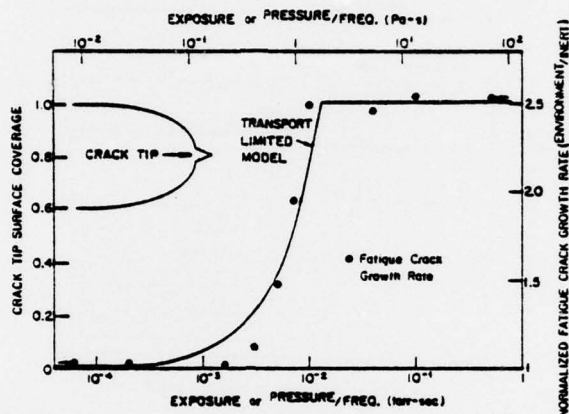


Fig. 9. Comparison between the observed fatigue crack growth response, for 2219-T851 aluminum alloy tested in water vapor at room temperature, and prediction of a transport-limited model. (After Wei and coworkers, 1979.)

These recent studies have contributed significantly to the phenomenological understanding of environment assisted fatigue crack growth. Correlation between the surface reaction kinetics and the dependence of fatigue crack growth response (below  $K_{Isc}$ ) as a function of frequency and water vapor pressure has now been established for these two very different alloy-environment systems. Two separate regimes can now be identified, where environment enhancement of fatigue crack growth is determined by the extent of surface reaction during one loading cycle. For alloy-environment systems with "slow" reaction kinetics (e.g., steel-water vapor system), environmental effects are evident at "high" pressures and "low" frequencies, and crack growth enhancement is only a function of the surface reaction kinetics. For alloy-environment systems with "fast" reaction kinetics (e.g., aluminum-water vapor system), on the other hand, environmental effects now manifest themselves at "low" pressures and "high" frequencies, and the enhancement of crack growth now also depends on the rate of transport of the external environment to the crack tip. The 3 orders of magnitude difference between the rates of water vapor reactions with aluminum alloys and with steels (compare Figs. 3 and 8) can readily account for the observed differences in environment assisted fatigue crack growth response for these alloys (Hudak and Wei, 1972). The correlation developed in these studies (Pao, Wei and Wei, 1978; Wei and coworkers, 1979) appears to have general applicability for the enhancement of fatigue crack growth in gaseous environments, and provides a basis for assessing environmental effects. Extension of the basic concept and approach to the consideration of cracking problems in aqueous environments should prove to be useful and is being explored.

### MODELING AND ENGINEERING IMPLICATIONS

Based on the recently developed understanding and on research over the past 15 years, a rational basis for treating environment assisted fatigue crack growth has been suggested (Wei, 1979). The rate of fatigue crack growth in an aggressive environment,  $(da/dN)_e$ , is considered to be the sum of three components.

$$\begin{aligned}(da/dN)_e &= (da/dN)_f + (da/dN)_{cf} + (da/dN)_{scc} \\ &= (da/dN)_f + (da/dN)_{cf} + \int_0^T [da/dt(K)] dt\end{aligned}$$

$(da/dN)_f$  is the rate of fatigue crack growth in an inert environment and, therefore, represents the contribution of "pure" (mechanical) fatigue. This component is essentially independent of frequency at temperatures where creep is not important.  $(da/dN)_{cf}$  represents a cycle-dependent contribution requiring synergistic interaction of fatigue and environmental attack.  $(da/dN)_{scc}$  is the contribution by sustained-load crack growth (that is, stress corrosion cracking) at K levels above  $K_{Iscc}$  (Wei and Landes, 1969).

Detailed examinations of the contribution by sustained-load crack growth, that is the  $(da/dN)_{scc}$  term, have been made previously (Miller, Hudak and Wei, 1973; Wei and Landes, 1969). For usual engineering applications, however, alloys that are highly susceptible to sustained-load crack growth (stress corrosion cracking) would not be used, and the  $(da/dN)_{scc}$  term is primarily of academic interest. The cycle-dependent term,  $(da/dN)_{cf}$ , on the other hand, is quite important. Its existence has been recognized by researchers for some time (Barsom, 1972; Gallagher, 1971; Parkins and Greenwell, 1977; Speidel and coworkers, 1972; Wei, 1970). A formal framework for estimating the frequency and pressure dependence in gaseous environments is beginning to emerge.

The cycle-dependent term, however, has not been fully appreciated by most of the engineering community. Its impact must be recognized and taken into account in the development of design data, and particularly in the use of the so-called accelerated tests. By the same token, reliability of service life predictions depend on a proper accounting of the environmentally induced effects.

### SUMMARY

Recent fracture mechanics and surface chemistry based studies have contributed to further understanding of environment assisted fatigue crack growth in high-strength alloys. The rate of fatigue crack growth in an aggressive environment,  $(da/dN)_e$ , may be considered to be the sum of three components.

$$(da/dN)_e = (da/dN)_f + (da/dN)_{cf} + (da/dN)_{scc}$$

$(da/dN)_f$  is the rate of fatigue crack growth in an inert environment, and, therefore, represents the contribution of "pure" fatigue.  $(da/dN)_{cf}$  represents a cycle-dependent contribution requiring synergistic interaction of fatigue and environmental attack.  $(da/dN)_{scc}$  is the contribution by sustained-load crack growth (i.e., stress corrosion cracking) at K levels above  $K_{Iscc}$ . The cycle-dependent term has been shown to arise from the reaction of the environment with fresh crack surfaces produced by fatigue, and is a function of the extent of reaction during one loading cycle. For highly reactive alloy-environment systems, cracking response may depend also on the rate of transport of the aggressive environment to the crack tip. For gaseous environments, a formal basis for estimating pressure and frequency dependence has been developed. The framework and approach are expected to be

applicable to other aggressive environments (such as, aqueous environments), and should provide a basis for the development of appropriate material evaluation and life prediction procedures.

#### ACKNOWLEDGEMENT

Support of this work by the Office of Naval Research under Contract N00014-75-C-0543, NR 036-097 is gratefully acknowledged.

#### REFERENCES

- Barsom, J. M. (1972). In Corrosion Fatigue, NACE-2, 424-436.
- Bradshaw, F. J. and Wheeler, C. (1968). RAE Tech. Rep. No. 68041.
- Brown, B. F. and Beachem, C. D. (1965). Corr. Sci., 5, 745-750.
- Corrosion Fatigue (1972). NACE-2, O. F. Devereux, A. J. McEvily & R. W. Staehle, (Eds.).
- Dwyer, D. J., Simmons, G. W. and Wei, R. P. (1977). Surf. Sci., 64, 617-632.
- Fatigue Crack Propagation (1967). ASTM STP 415.
- Gallagher, J. P. (1971). J. of Mater., JMLSA, ASTM, 6, 941.
- Gallagher, J. P. and Wei, R. P. (1972). In Corrosion Fatigue, NACE-2, 409-423.
- Hartman, A. and Jacobs, F. J., Nederveen, A. and DeRijk, R. (1967). NLR Tech. Note No. M. 2182.
- Hudak, S. J. and Wei, R. P. (1972). In Corrosion Fatigue, NACE-2, 433-434.
- McEvily, A. J. and Wei, R. P. (1972). In Corrosion Fatigue, NACE-2, 381-395.
- Miller, G. A., Hudak, S. J. and Wei, R. P. (1973). J. Testing & Evaluation, ASTM, 1, 524-530.
- Pao, P. S., Wei, W. and Wei, R. P. (1979). Effect of frequency on fatigue crack growth response of AISI 4340 steel in water vapor. Proceedings of Symposium on Environment Sensitive Fracture of Engineering Materials (TSM-AIME), to be published.
- Parkins, R. N. and Greenwell, B. S. (1977). Metal Sci., August/Sept., 405-413.
- Speidel, M. O., Blackburn, M. J., Beck, T. R. and Feeney, J. A. (1972). In Corrosion Fatigue, NACE-2, 324-345.
- Simmons, G. W., Pao, P. S. and Wei, R. P. (1978). Met. Trans. A, 9A, 1147-1158.
- Wei, R. P. (1968). Int. J. Fract. Mech., 4, 159-170.
- Wei, R. P. (1970). J. Eng. Fract. Mech., 1, 633-651.
- Wei, R. P. (1979). On understanding environment enhanced fatigue crack growth - a fundamental approach. Symposium on Fatigue Mech., ASTM, to be published.
- Wei, R. P. and Landes, J. D. (1969). Int. J. Fract. Mech., 5, 69-71.
- Wei, R. P., Novak, S. R. and Williams, D. P. (1972). Mater. Res. & Stds., ASTM, 12, 9, 25-30.
- Wei, R. P. and Simmons, G. W. (1976). Scripta Met., 10, 153-157.
- Wei, R. P. and Simmons, G. W. (1977). In Stress Corrosion Cracking and Hydrogen Embrittlement of Iron Base Alloys, NACE-5, 751-765.
- Wei, R. P., Simmons, G. W., Hart, R. G., Pao, P. S. and Weir, T. (1979). Fracture mechanics and surface chemistry studies of fatigue crack growth in an aluminum alloy. To be published.
- Wei, R. P. and Speidel, M. O. (1972). In Corrosion Fatigue, NACE-2, 379-380.
- Wei, R. P., Taldi, P. M. and Li, Che-Yu (1967). In Fatigue Crack Propagation, ASTM STP 415, 460-480.
- Williams, D. P., III, Pao, P. S. and Wei, R. P. (1979). The combined influence of chemical, metallurgical and mechanical factors on environment assisted cracking. Proceedings of Symposium on Environment Sensitive Fracture of Engineering Materials (TSM-AIME), to be published.

# BASIC DISTRIBUTION LIST

Technical and Summary Reports

April 1978

<u>Organization</u>	<u>Copies</u>	<u>Organization</u>	<u>Copies</u>
Defense Documentation Center Cameron Station Alexandria, VA 22314	12	Naval Air Propulsion Test Center Trenton, NJ 08628 ATTN: Library	1
Office of Naval Research Department of the Navy 800 N. Quincy Street Arlington, VA 22217		Naval Construction Battalion Civil Engineering Laboratory Port Hueneme, CA 93043 ATTN: Materials Division	1
ATTN: Code 471	1	Naval Electronics Laboratory San Diego, CA 92152	
Code 102	1	ATTN: Electron Materials Sciences Division	1
Code 470	1		
Commanding Officer Office of Naval Research Branch Office Building 114, Section D 666 Summer Street Boston, MA 02210	1	Naval Missile Center Materials Consultant Code 3312-1 Point Mugu, CA 92041	1
Commanding Officer Office of Naval Research Branch Office 536 South Clark Street Chicago, IL 60605	1	Commanding Officer Naval Surface Weapons Center White Oak Laboratory Silver Spring, MD 20910 ATTN: Library	1
Office of Naval Research San Francisco Area Office 760 Market Street, Room 447 San Francisco, CA 94102	1	David W. Taylor Naval Ship Research and Development Center Materials Department Annapolis, MD 21402	1
Naval Research Laboratory Washington, DC 20375		Naval Undersea Center San Diego, CA 92132 ATTN: Library	1
ATTN: Codes 6000	1	Naval Underwater System Center Newport, RI 02840	
6100	1	ATTN: Library	1
6300	1		
6400	1	Naval Weapons Center China Lake, CA 93555	
2627	1	ATTN: Library	1
Naval Air Development Center Code 302 Warminster, PA 18964 ATTN: Mr. F. S. Williams	1	Naval Postgraduate School Monterey, CA 93940 ATTN: Mechanical Engineering Department	1

# BASIC DISTRIBUTION LIST (cont'd)

<u>Organization</u>	<u>Copies</u>	<u>Organization</u>	<u>Copies</u>
Naval Air Systems Command Washington, DC 20360 ATTN: Codes 52031 52032	1	NASA Headquarters Washington, DC 20546 ATTN: Code:RRM	1
Naval Sea System Command Washington, DC 20362 ATTN: Code 035	1	NASA Lewis Research Center 21000 Brookpark Road Cleveland, OH 44135 ATTN: Library	1
Naval Facilities Engineering Command Alexandria, VA 22331 ATTN: Code 03	1	National Bureau of Standards Washington, DC 20234 ATTN: Metallurgy Division Inorganic Materials Div.	1 1
Scientific Advisor Commandant of the Marine Corps Washington, DC 20380 ATTN: Code AX	1	Director Applied Physics Laboratory University of Washington 1013 Northeast Forthieth Street Seattle, WA 98105	1
Naval Ship Engineering Center Department of the Navy Washington, DC 20360 ATTN: Code 6101	1	Defense Metals and Ceramics Information Center Battelle Memorial Institute 505 King Avenue Columbus, OH 43201	1
Army Research Office P.O. Box 12211 Triangle Park, NC 27709 ATTN: Metallurgy & Ceramics Program	1	Metals and Ceramics Division Oak Ridge National Laboratory P.O. Box X Oak Ridge, TN 37380	1
Army Materials and Mechanics Research Center Watertown, MA 02172 ATTN: Research Programs Office	1	Los Alamos Scientific Laboratory P.O. Box 1663 Los Alamos, NM 87544 ATTN: Report Librarian	1
Air Force Office of Scientific Research Bldg. 410 Bolling Air Force Base Washington, DC 20332 ATTN: Chemical Science Directorate Electronics & Solid State Sciences Directorate	1 1	Argonne National Laboratory Metallurgy Division P.O. Box 229 Lemont, IL 60439	1
Air Force Materials Laboratory Wright-Patterson AFB Dayton, OH 45433	1	Brookhaven National Laboratory Technical Information Division Upton, Long Island New York 11973 ATTN: Research Library	1
Library Building 50, Rm 134 Lawrence Radiation Laboratory Berkeley, CA	1	Office of Naval Research Branch Office 1030 East Green Street Pasadena, CA 91106	1

C  
April 1978

## SUPPLEMENTARY DISTRIBUTION LIST

### Technical and Summary Reports

Dr. T. R. Beck  
Electrochemical Technology Corporation  
10035 31st Avenue, NE  
Seattle, Washington 98125

Professor I. M. Bernstein  
Carnegie-Mellon University  
Schenley Park  
Pittsburgh, Pennsylvania 15213

Professor H. K. Birnbaum  
University of Illinois  
Department of Metallurgy  
Urbana, Illinois 61801

Dr. Otto Buck  
Rockwell International  
1049 Camino Dos Rios  
P.O. Box 1085  
Thousand Oaks, California 91360

Dr. David L. Davidson  
Southwest Research Institute  
8500 Culebra Road  
P.O. Drawer 28510  
San Antonio, Texas 78284

Dr. D. J. Duquette  
Department of Metallurgical Engineering  
Rensselaer Polytechnic Institute  
Troy, New York 12181

Professor R. T. Foley  
The American University  
Department of Chemistry  
Washington, D.C. 20016

Mr. G. A. Gehring  
Ocean City Research Corporation  
Tennessee Avenue & Beach Thorofare  
Ocean City, New Jersey 08226

Dr. J. A. S. Green  
Martin Marietta Corporation  
1450 South Rolling Road  
Baltimore, Maryland 21227

Professor R. H. Heidersbach  
University of Rhode Island  
Department of Ocean Engineering  
Kingston, Rhode Island 02881

Professor H. Herman  
State University of New York  
Material Sciences Division  
Stony Brook, New York 11794

Professor J. P. Hirth  
Ohio State University  
Metallurgical Engineering  
Columbus, Ohio 43210

Dr. D. W. Hoepfner  
University of Missouri  
College of Engineering  
Columbia, Missouri 65201

Dr. E. W. Johnson  
Westinghouse Electric Corporation  
Research and Development Center  
1310 Beulah Road  
Pittsburgh, Pennsylvania 15235

Professor R. M. Latanision  
Massachusetts Institute of Technology  
77 Massachusetts Avenue  
Room E19-702  
Cambridge, Massachusetts 02139

Dr. F. Mansfeld  
Rockwell International Science Center  
1049 Camino Dos Rios  
P.O. Box 1085  
Thousand Oaks, California 91360

Professor A. E. Miller  
University of Notre Dame  
College of Engineering  
Notre Dame, Indiana 46556

Dr. Jeff Perkins  
Naval Postgraduate School  
Monterey, California 93940

C  
April 1978

SUPPLEMENTARY DISTRIBUTION LIST  
(Continued)

Professor H. W. Pickering  
Pennsylvania State University  
Department of Material Sciences  
University Park, Pennsylvania 16802

Professor R. W. Staehle  
Ohio State University  
Department of Metallurgical Engineering  
Columbus, Ohio 43210

Dr. E. A. Starke, Jr.  
Georgia Institute of Technology  
School of Chemical Engineering  
Atlanta, Georgia 30332

Dr. Barry C. Syrett  
Stanford Research Institute  
333 Ravenswood Avenue  
Menlo Park, California 94025

Dr. R. P. Wei  
Lehigh University  
Institute for Fracture and  
Solid Mechanics  
Bethlehem, Pennsylvania 18015

Professor H. G. F. Wilsdorf  
University of Virginia  
Department of Materials Science  
Charlottesville, Virginia 22903